

Test Report

Compression Properties of Hunt Pipeline Filler Compound #805 Fast Set Dent Fill

September 24, 2022

Prepared by

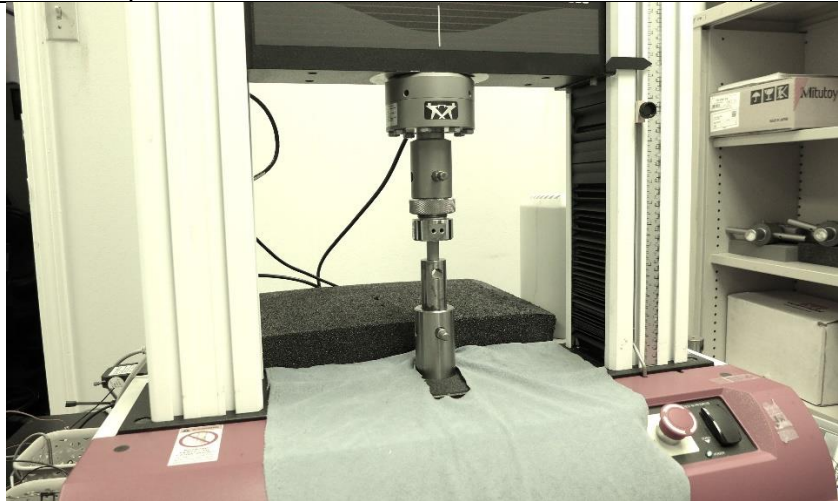
Benjamin T. A. Chang, PhD, PE, FNACE
President of PolyLab
3rd Party Coating Test Lab, Coating Expert Witness
Certified NACE Protective Coating Specialist
Certified AMPP Coating Inspector
Houston, TX 77042
(713) 783-7659
PolyLab@gmail.com
www.PolyLabLLC.com

Test Report

Compression Properties of Hunt Pipeline Filler Compound #805 Fast Set Dent Fill

By Benjamin T. A. Chang, PhD, PE, FNACE, President of PolyLab

1. Test Method

Test Standard	ASTM D695
Crosshead Speed	0.05 inch/min
Test Temperature	25 C
	
<p>Filler Cylinder Sample under compression</p>	

2. Test Result

Sample #	OD, in	Length, in	Modulus, ksi	Compressive Strength, ksi
#1	0.6120	0.9510	220	8.85
#3	0.6055	0.9615	190	9.34
#4	0.6225	0.9645	251	9.47
#5	0.6070	0.9565	265	9.76
#6	0.6075	0.9575	260	10.32
Mean	0.6109	0.9582	237	9.55
Std Dev	0.0069	0.0051	32	0.54