

# Test Report

**Compression Properties of Hunt Pipeline Filler Compound # 650 Annulus Fill**

October 5, 2022

Prepared by

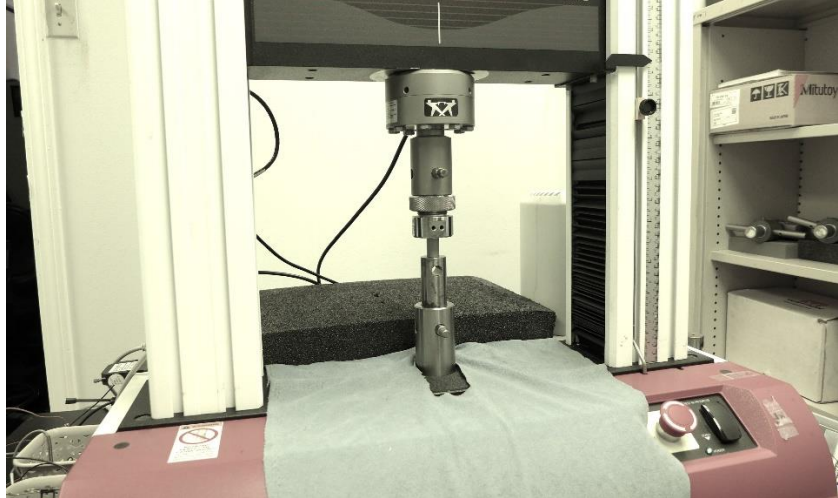
Benjamin T. A. Chang, PhD, PE, FNACE  
President of PolyLab  
3<sup>rd</sup> Party Coating Test Lab, Coating Expert Witness  
Certified NACE Protective Coating Specialist  
Certified AMPP Coating Inspector  
10400 Westoffice Dr. Ste 106  
Houston, TX 77042  
(713) 783-7659  
[PolyLab@gmail.com](mailto:PolyLab@gmail.com)  
[www.PolyLabLLC.com](http://www.PolyLabLLC.com)

# Test Report

## Compression Properties of Hunt Pipeline Filler Compound # 650 Annulus Fill

By Benjamin T. A. Chang, PhD, PE, FNACE, President of PolyLab

### 1. Test Method

Test Standard	ASTM D695
Crosshead Speed	0.05 inch/min
Test Temperature	25 C
	
<p>Filler Cylinder Sample under compression</p>	

### 2. Test Result

Sample #	OD, in	Length, in	Modulus, ksi	Compressive Strength, ksi
A	0.6145	1.0435	151	5.19
B	0.6145	1.0425	153	5.24
C	0.6195	1.0435	146	5.05
D	0.6155	1.0435	145	5.03
E	0.612	1.0435	151	5.19
Mean	0.6152	1.0433	149	5.14
Std Dev	0.0027	0.0004	3	0.09